


Speeds and Feeds for Drill Mills

Fractional

* Through Hole *

Type	Rc Hardness	SFM (Vc)		CHIPLOAD PER FLUTE (Fz)			
		152M, 152MA 154M, 154MA	152D, 152DA	1/8" - 1/4"	1/4" - 3/8"	3/8" - 1/2"	1/2" - 3/4"
TITANIUM ALLOYS							
Commercially Pure, 6Al-4V, Astm 1/2/3, 6Al-25N-4Zr-2Mo-Si		-	125 - 250	.0007" - .0015"	.0010" - .0025"	.0015" - .0040"	.0030" - .0050"
STAINLESS STEELS							
13/8, 15/5, 17-4, pH Types	< 35 > 35	- -	100 - 150 80 - 150	.0005" - .0010" .0003" - .0005"	.0008" - .0020" .0005" - .0015"	.0010" - .0030" .0010" - .0020"	.0020" - .0040" .0010" - .0030"
HIGH STRENGTH TOOL STEELS							
4140, 4340, 6150, 5210, A2, D2, P20, H11, H13, S2, O1	< 30 30 - 38	-	125 - 175 80 - 120	.0005" - .0010" .0003" - .0005"	.0008" - .0020" .0005" - .0015"	.0010" - .0030" .0010" - .0020"	.0020" - .0040" .0010" - .0030"
MEDIUM ALLOY TOOL STEELS							
200, 250, 300, 8620	< 35 > 35	- -	150 - 200 100 - 150	.0007" - .0015" .0005" - .0010"	.0010" - .0025" .0008" - .0020"	.0015" - .0040" .0010" - .0030"	.0030" - .0050" .0020" - .0040"
CARBON STEELS							
A36, 12L14, 1000's, 1100's, 1300's	< 35 > 35	175 - 250 -	150 - 200 100 - 150	.0007" - .0015" .0005" - .0010"	.0010" - .0025" .0008" - .0020"	.0015" - .0040" .0010" - .0030"	.0030" - .0050" .0020" - .0040"
CAST MATERIAL							
Steel		-	175 - 250	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"	.0030" - .0060"
Ductile Iron		-	175 - 250	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"	.0030" - .0060"
Gray Iron		-	175 - 250	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"	.0030" - .0060"
Aluminum		250 - 350	250 - 350	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"	.0030" - .0060"
ALUMINUM							
Aircraft Grade (6061, 7075)		350 - 500	300 - 400	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"	.0030" - .0060"
MAGNESIUM							
		250 - 400	250 - 350	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"	.0030" - .0060"
COPPER							
Copper Alloys		250 - 350	150 - 300	.0007" - .0015"	.0010" - .0025"	.0015" - .0035"	.0020" - .0050"
BRASS, BRONZE							
Brass, Aluminum/Bronze, Low Silicon Bronze		250 - 350	150 - 300	.0007" - .0015"	.0010" - .0025"	.0015" - .0035"	.0020" - .0050"
COMPOSITE MATERIAL							
Glass Epoxy, Fiberglass, Plastics		250 - 450	200 - 400	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"	.0030" - .0060"
Graphite, G10, Carbon Fiber		300 - 500	250 - 450	.0010" - .0020"	.0015" - .0030"	.0020" - .0040"	.0030" - .0060"

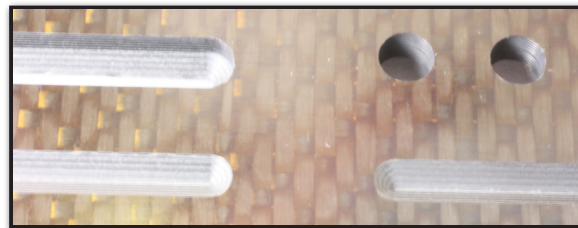

NOTE - ABOVE ARE STARTING PARAMETERS ONLY. HIGHER RESULTS MAY BE ACHIEVED WITH OPTIMUM CONDITIONS.